

CrossMark  
click for updates

## Au@Ag core/shell nanoparticles as colorimetric probes for cyanide sensing†

Cite this: DOI: 10.1039/c4nr02560a

Jing-bin Zeng,<sup>\*a</sup> Ying-ying Cao,<sup>a</sup> Jing-jing Chen,<sup>a</sup> Xu-dong Wang,<sup>b</sup> Jian-feng Yu,<sup>a</sup> Bin-bin Yu,<sup>c</sup> Zi-feng Yan<sup>\*a</sup> and Xi Chen<sup>d</sup>Received 11th May 2014  
Accepted 26th June 2014

DOI: 10.1039/c4nr02560a

www.rsc.org/nanoscale

We synthesize Au@Ag core/shell nanoparticles (NPs) using a Au NP assisted Tollens reaction. The as-synthesized NPs are used for the colorimetric cyanide sensing with a detection limit of 0.4  $\mu\text{M}$ . The bimetallic NPs are immobilized into agarose gels as portable “test strips”.


The cyanide anion is highly toxic to mammals, since it can strongly bind with  $\text{Fe}^{3+}$  of heme cofactors in  $\text{a}_3$  cytochrome to rapidly deactivate its oxygen transport function.<sup>1</sup> Nevertheless, cyanide is widely used in several industrial activities, particularly in electroplating, metallurgy and organic polymer production,<sup>2</sup> which raises the risk of its contamination to environmental water. A variety of receptors or sensors have been developed to bind or sense cyanide.<sup>2–4</sup> These chemosensors are based on either an organic chemophore or a metal complex, which reacts or coordinates with cyanide to induce spectral changes.<sup>5–7</sup> Despite the good sensitivity and selectivity obtained for cyanide, drawbacks such as laborious organic synthesis,<sup>6a–c,7c</sup> poor water compatibility<sup>6e–h</sup> and/or long reaction times limit their practical application.

Cyanide is able to dissolve metals like gold and silver in the presence of oxygen *via* the formation of a metal–cyanide complex.<sup>8</sup> Taking advantage of this property, a number of gold (Au) and silver (Ag) nanoparticles (NPs) based fluorescent probes have been explored for cyanide sensing.<sup>9</sup> For instance, cyanide can induce the dissolution of dye-adsorbed Au NPs, which enables a sensitive “turn-on” fluorescence detection of cyanide.<sup>9b,c</sup> These approaches allow the detection of cyanide in

pure aqueous medium with high sensitivity, but rely on specialized equipment and considerable skills. Therefore, the development of a simple, rapid, sensitive and selective sensing system that allows the visual readout of cyanide in real samples is still highly imperative.

The surface plasma resonance (SPR) of Au@Ag core/shell nanostructures is highly dependent on the dimensional shell-to-core ratio,<sup>10</sup> and therefore its slight variation often leads to an obvious spectral and/or color change. This property prompts us to develop a cyanide detection approach based on Au@Ag core/shell NPs, since cyanide is expected to be able to modify the dimensional shell-to-core ratio by sequentially dissolving silver shells and gold cores as shown in Scheme 1 and as a result, one can tune the shape of absorption spectra. The corresponding apparent color changes are also in direct relation to the cyanide concentration, and thus can be utilized for colorimetric detection of cyanide.

The Au@Ag core/shell NPs were synthesized using citrate capped Au NPs coupled with the classic Tollens reaction, in

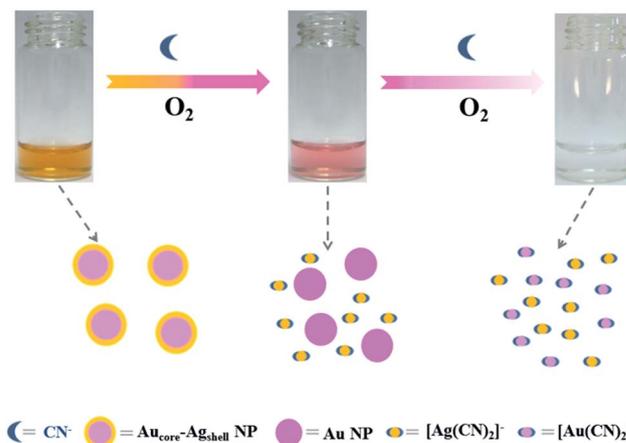

Scheme 1 Schematic diagram of the Au@Ag core/shell NPs for the colorimetric detection of cyanide.

<sup>a</sup>State Key Laboratory of Heavy Oil Processing and College of Science, China University of Petroleum (East China), Qingdao, 266555, China. E-mail: xmuzjb@163.com

<sup>b</sup>Institute for Biological Interfaces, Karlsruhe Institute of Technology, 76344 Karlsruhe, Germany

<sup>c</sup>Environmental Monitoring Centre of Taizhou, Taizhou 318000, China

<sup>d</sup>College of Chemistry and Chemical Engineering, Xiamen University, Xiamen 361005, China

† Electronic supplementary information (ESI) available: Experimental procedures and Fig. S1–S14. See DOI: 10.1039/c4nr02560a

which the silver nanoshells generated from the Tollens reaction are deposited over the Au NPs.<sup>11</sup> Fig. 1a–c reveal that most of the bimetallic NPs were spherical and exhibited electronic inhomogeneity with a dark core surrounded by a lighter shell. An overlay of energy-dispersive X-ray spectroscopic (EDX) maps on a representative bimetallic NP (Fig. 1d) indicates the presence of gold and silver elements, which are primarily located at the central and outer part, respectively. The size distribution histogram of the as-prepared Au@Ag core/shell NPs is given in Fig. S1,<sup>†</sup> and their mean sizes were  $21.8 \pm 2.5$  nm. The zeta potential of the Au@Ag core/shell NPs was measured to be  $-40.8$  mV, which was similar to that of Au NPs ( $-43.8$  mV). These results implied that the surface of Au@Ag core/shell NPs was also probably capped by the negative citrate, which can stabilize the NPs against aggregation with electrostatic repulsion.<sup>12</sup> The as-synthesized NPs can be stable within the pH range of 5–11 without aggregation (Fig. S2<sup>†</sup>).

In view of the sensing mechanism mentioned above, the performance of the colorimetric assay probably depends on the silver shell thickness, which is related to the concentration of the Tollens reagent ( $[\text{Ag}(\text{NH}_3)_2]\text{OH}$ ) and HCHO. As shown in Fig. S3,<sup>†</sup> we prepared Au@Ag core/shell NPs with thicker shells by increasing the concentration of HCHO. Fig. S4 indicates that the core/shell NPs with thick silver shells were beneficial for the detection of cyanide in a wide concentration range, but they suffered from low sensitivity and visual resolution. In contrast, the NPs with thin silver shells were sensitive for the detection of cyanide, but the tunable color range was narrow (Fig. S5<sup>†</sup>). The optimum concentrations of  $[\text{Ag}(\text{NH}_3)_2]\text{OH}$  and HCHO were found to be 0.24 and 0.96 mM, respectively, to prepare the core/shell NPs with the average thickness of silver shells at 4.4 nm (Fig. S1<sup>†</sup>).<sup>13</sup> The concentration of Au NPs is also an important factor that can affect the tunable color range of the assay, which was optimized to be 1.2 nm (data not shown). The pH effect on the colorimetric assay was investigated from 8 to 11, because cyanide tends to be converted into volatile HCN under acidic

and even neutral conditions. It can be seen from Fig. S6<sup>†</sup> that the colorimetric assay exhibited the best sensitivity for cyanide at pH 9.<sup>†</sup>

We then used the colloidal Au@Ag core/shell NPs for the detection of cyanide. With the addition of increasing concentrations of cyanide, the color of the colloidal solution turned from yellow to orange, pink, and finally colorless (Fig. 2a), which enables visual detection of cyanide using bare eyes. The lowest concentration of cyanide that can be visually distinguished was 1.2  $\mu\text{M}$ , which is lower than 1.9  $\mu\text{M}$ , *i.e.* the maximum allowable concentration of cyanide in drinking water regulated by the World Health Organization.<sup>14</sup> For comparison, monometallic Ag NPs and Au NPs were synthesized and used for cyanide detection. As shown in Fig. 2b and c, both of these nanoproboscopes were also applicable for colorimetric cyanide detection as reported elsewhere<sup>15</sup> but suffered from low visual resolution. The use of core/shell nanoparticles significantly increases the color gradient, and thus improves visual resolution. Fig. 2d shows that the absorbance at 394 nm ( $A_{394}$ ) decreased with the increase of cyanide concentration, and there was a linear relationship between the  $\Delta A_{394}$  and cyanide concentrations in the range of 0.4–100  $\mu\text{M}$ . The lowest detectable concentration was 0.4  $\mu\text{M}$ , which is comparable to or even lower than those of fluorescence-based methods (Table S1<sup>†</sup>). Such high sensitivity of this method is ascribed to the fact that cyanide is extremely reactive to silver and gold, and therefore a small amount of cyanide can modify significantly

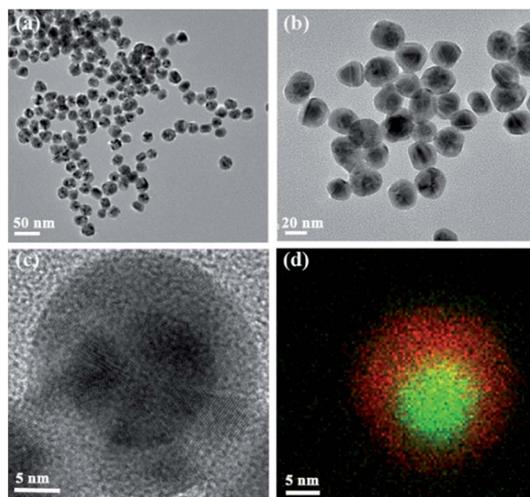


Fig. 1 (a and b) TEM images (c) a typical HR-TEM image and (d) an EDX elemental map shown as the overlay of the Au and Ag signal of Au@Ag core/shell NPs.

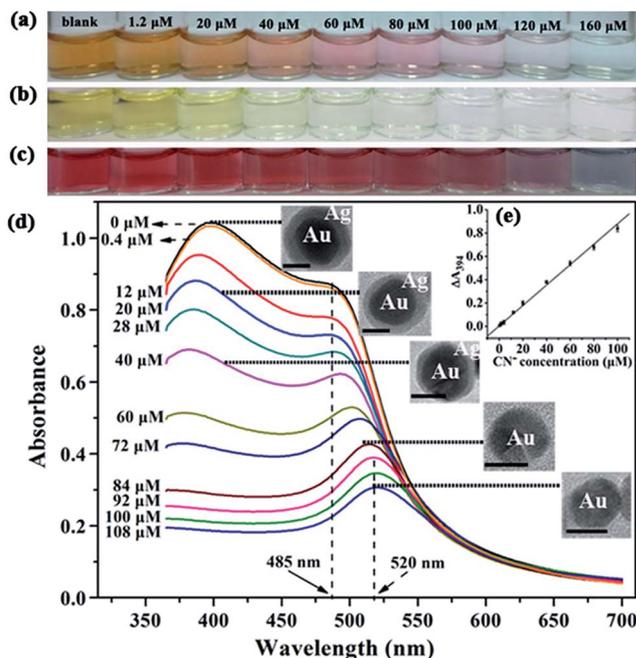


Fig. 2 Photographs of the (a) Au@Ag core/shell NPs (b) Ag NPs and (c) Au NPs with the addition of various amounts of cyanide; (d) UV-vis spectra of the Au@Ag core/shell NPs with the addition of increasing cyanide; the inset in (d) represents the corresponding TEM images of the Au@Ag core/shell NPs treated with different amounts of cyanide; the black scale bar represents the length of 10 nm and (e) the linear plot of  $\Delta A_{394}$  versus the cyanide concentration.

the dimensional shell-to-core ratio of Au@Ag NPs, leading to an observable change in both the apparent color and the shape of absorption spectra. Fig. S7† shows that the response time of the approach was less than one minute. The reproducibility of the method was satisfactory with the relative standard deviation being less than 2.3% (Fig. S8†).

To get insight into the mechanisms of the proposed approach, the spectra of the Au@Ag core/shell NPs with and without cyanide treatment were correlated with their geometric dimensions (Fig. 2b inset and Fig. S9†). Fig. 2b shows that, as the cyanide concentration increases from 0 to 40  $\mu\text{M}$ , the intensity of the high-energy SPR peak originating from silver shells continuously decreased, while the low-energy SPR peak belonging to gold cores progressively red-shifted, indicating the dissolution of silver shells. TEM studies also reveal that the thickness of silver shells decreased progressively from  $\sim 4.4$  to  $\sim 2.8$  and  $\sim 1.4$  nm, while the size of gold cores remained almost constant. When the cyanide concentration reached 92  $\mu\text{M}$ , the low-energy SPR peak disappeared and the high-energy SPR peak red-shifted to 520 nm, which is the typical plasmon resonance peak of Au NPs. The corresponding TEM image also revealed the disappearance of silver shells and the exposure of gold cores. These results indicated that at a cyanide concentration of 92  $\mu\text{M}$ , silver shells were completely dissolved, while the gold cores were thoroughly exposed but had barely been etched. As the cyanide concentration increased further, the low-energy SPR peak intensity continued to decrease but without any red shift, indicating the inceptive etching of gold cores. TEM studies also reveal that the size of Au NPs decreased from  $\sim 13.0$  to  $\sim 12.1$  nm when the cyanide concentration reached 108  $\mu\text{M}$ . These findings demonstrate that cyanide progressively dissolved silver shells and gold cores of Au@Ag core/shell NPs.

Inductively coupled plasma mass spectrometry (ICP-MS) was used to determine the silver and gold content in the Au@Ag core/shell NP colloidal solution before and after cyanide treatment. High-speed centrifugation (16 000 rpm) was used to precipitate the NPs, and the supernatant was collected for the analysis. As listed in Table S2,† when the cyanide concentration increased from 0 to 92  $\mu\text{M}$ , the silver and gold content increased from 0.29 to 7.0  $\text{mg L}^{-1}$  and from 0.49 to 12.5  $\text{mg L}^{-1}$ , respectively. Electrospray ionization time-of-flight (ESI-TOF) mass spectrometry was used to confirm the product generated by the reaction between Au@Ag core/shell NPs and cyanide. Fig. 3 shows that no gold- or silver-cyanide complex can be detected before cyanide treatment, while both of them were detected with the addition of increasing concentrations of cyanide. The two peaks appearing at  $m/z$  158.92 and 160.92 belonged to  $[\text{Ag}(\text{CN})_2]^-$ , while that of 248.98 corresponded to  $[\text{Au}(\text{CN})_2]$ .

To examine the specificity of the approach, its response to cyanide as well as several other common anions and cations was investigated. Fig. 4 indicates that only the addition of cyanide into Au@Ag core/shell colloidal solution induced an apparent color change from yellow to pink and a significant decrease of absorbance at 394 nm. The coexistence of at least 25-fold excess of other anions (except the case of iodide) hardly affected the determination of cyanide. A mixture of eighteen anions also has no significant effect on cyanide detection. Such good selectivity

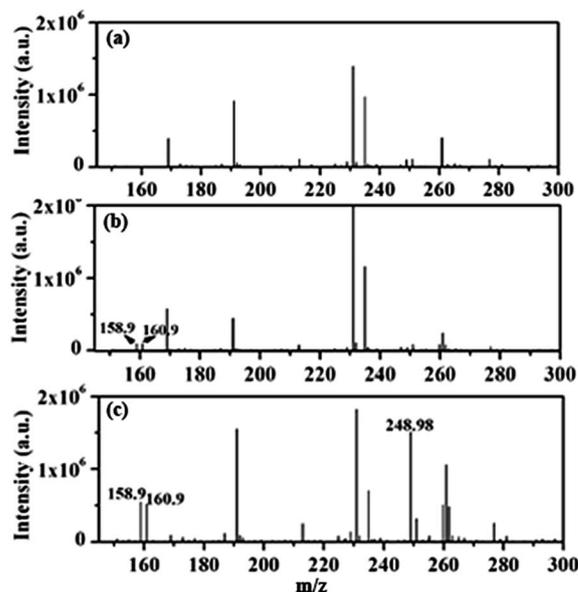


Fig. 3 The ESI-MS spectra of the supernatant of Au@Ag core/shell NPs with the addition of cyanide at (a) 0 (b) 8 and (c) 120  $\mu\text{M}$ .

can be attributed to the unique reaction between cyanide and silver or gold as discussed above. The maximum interference was caused by one equiv. of iodide (80  $\mu\text{M}$ ), but the induced signal was still 9.2-fold lower than that of cyanide. Moreover, it must be emphasized that the iodide concentration in natural water samples is always very low. For example, even sea water generally contains iodide at less than 1  $\mu\text{M}$ .<sup>9f</sup> Fig. S10† shows that the responses induced by some common cations were at

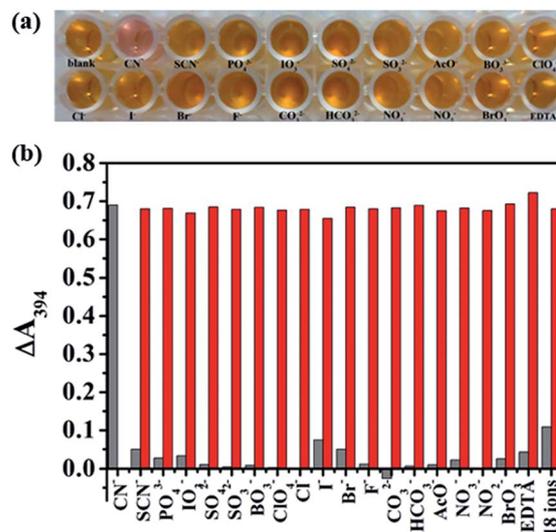


Fig. 4 (a) Photographs and (b) decreased absorbance at 394 nm ( $\Delta A_{394}$ ) of the Au@Ag core/shell NPs with the addition of different anions. Gray bars represent the  $\Delta A_{394}$  of the Au@Ag core/shell NPs in the presence of different anions, red bars represent the  $\Delta A_{394}$  of Au@Ag core/shell NPs in the co-existence of cyanide and other anions. The concentration was 80  $\mu\text{M}$  for cyanide and iodide, 2 mM for phosphate and 4 mM for other anions.

least 12.5-fold lower than that of cyanide. Furthermore, using EDTA as a masking agent, even 20 equiv. of cations shows little interfering effect (Fig. S11†).

We immobilized the Au@Ag core/shell NPs into agarose gels and used them for the colorimetric detection of cyanide in aqueous medium. As can be seen in Fig. S12a,† the colors of the agarose gels changed from yellow to orange, pink and finally colorless, which were very similar to those obtained in solutions. These agarose gels were directly used for UV-vis analysis (Fig. S12b†), and there was a linear relationship between  $\Delta A_{394}$  and cyanide concentration ranging from 8 to 80  $\mu\text{M}$  (Fig. S12c†). These results reveal the feasibility of the agarose gels for cyanide detection in terms of not only semi-quantitative colorimetric measurement but also quantitative determination. Nevertheless, it must be noted that the reaction process in the gel was much slower than that in the solution. This is probably due to the slower diffusion rate of the cyanide ion in agarose gels. We further used these agarose gels for the analysis of natural samples including tap, sea, lake and industrial water samples. Fig. 5 shows that the agarose gels exhibited similar color changes from yellow to pink and colorless for ultrapure and other natural water samples. It should be noted that all the samples are collected and directly analyzed without any pretreatment steps. These results demonstrated that the agarose gels were tolerant to the matrix effect from the natural water samples. By comparison, we found that it is infeasible to use the Au@Ag core/shell solution for the direct analysis of industrial, lake and sea water samples, owing to its propensity to aggregation in the presence of high salinity.<sup>16</sup> Such a disadvantage has been overcome by immobilizing the NP system into the agarose gel. In addition, initial results indicated that our agarose gels were also applicable to the analysis of gaseous hydrogen cyanide in air (Fig. S13†) and cigarette smoke (Fig. S14†).

In summary, we propose a simple yet sensitive and selective cyanide detection approach by building Au@Ag core/shell nanostructures as a platform. The spectral behavior of Au@Ag

core/shell NPs is highly dependent on the shell-to-core ratio, and thus highly sensitive to cyanide leaching and, more importantly, the concurrent induced color changes could be easily observed with bare eyes. We immobilize the Au@Ag core/shell NPs into agarose gels, which have realized the direct analysis of cyanide in natural water samples without sample pretreatment steps. This work could be further extended to other Au@Ag core/shell nanomaterials such as nanocubes and nanorods, which might also be applicable for the colorimetric sensing of cyanide with corresponding different color changes.

## Acknowledgements

This work was financially supported by the National Nature Scientific Foundations of China (no. 21105123), the Shandong Young Scientist Awards (BS2012CL037) and the Fundamental Research Funds for the Central Universities (14CX02006A, 14CX02216A) which are gratefully acknowledged.

## Notes and references

- 1 J. L. Way, *Annu. Rev. Pharmacol. Toxicol.*, 1984, **24**, 451.
- 2 Z. Xu, X. Chen, H. N. Kim and J. Yoon, *Chem. Soc. Rev.*, 2010, **39**, 127.
- 3 J. Ma and P. K. Dasgupta, *Anal. Chim. Acta*, 2010, **673**, 117.
- 4 X. Lou, D. Ou, Q. Li and Z. Li, *Chem. Commun.*, 2012, **48**, 8462.
- 5 (a) P. Anzenbacher, D. S. Tyson, K. Jursikova and F. N. Castellano, *J. Am. Chem. Soc.*, 2002, **124**, 6232; (b) G. W. Lee, N. K. Kim and K. S. Jeong, *Org. Lett.*, 2010, **12**, 2634–2637.
- 6 (a) Y. Kim, H. Zhao and F. P. Gabbai, *Angew. Chem., Int. Ed.*, 2009, **48**, 4957; (b) S. Madhu, S. K. Basu, S. Jadhav and M. Ravikanth, *Analyst*, 2013, **138**, 299; (c) T. F. Robbins, H. Qian, X. Su, R. P. Hughes and I. Aprahamian, *Org. Lett.*, 2013, **15**, 2386; (d) J. Jo, A. Olasz, C. H. Chen and D. Lee, *J. Am. Chem. Soc.*, 2013, **135**, 3620; (e) M. Tomasulo and F. M. Raymo, *Org. Lett.*, 2005, **7**, 4633; (f) Y. K. Yang and J. S. Tae, *Org. Lett.*, 2006, **8**, 5721; (g) D. Cho, J. H. Kim and J. L. Sessler, *J. Am. Chem. Soc.*, 2008, **130**, 12163; (h) Q. Shu, L. Birlenbach and M. Schmittel, *Inorg. Chem.*, 2012, **51**, 13123; (i) X. Cheng, Y. Zhou, J. Qin and Z. Li, *ACS Appl. Mater. Interfaces*, 2012, **4**, 2133.
- 7 (a) X. Lou, L. Zhang, J. Qin and Z. Li, *Chem. Commun.*, 2008, **44**, 5848; (b) L. Tang, N. Wang, Q. Zhang, J. Guo and R. Nandhakumar, *Tetrahedron Lett.*, 2013, **54**, 536; (c) Y. Guo, X. Tang, F. Hou, J. Wu, W. Dou, W. Qin, J. Ru, G. Zhang, W. Liu and X. Yao, *Sens. Actuators, B*, 2013, **181**, 202.
- 8  $4\text{Ag} + 8\text{CN}^- + 2\text{H}_2\text{O} + \text{O}_2 \rightarrow 4[\text{Ag}(\text{CN})_2]^- + 4\text{OH}^-$ ,  $4\text{Au} + 8\text{CN}^- + 2\text{H}_2\text{O} + \text{O}_2 \rightarrow 4[\text{Au}(\text{CN})_2]^- + 4\text{OH}^-$ .
- 9 (a) Y. Liu, K. Ai, X. Cheng, L. Huo and L. Lu, *Adv. Funct. Mater.*, 2010, **20**, 951; (b) X. Lou, Q. Zeng, Y. Zhang, Z. Wan, J. Qin and Z. Li, *J. Mater. Chem.*, 2012, **22**, 5581; (c) L. Shang and S. Dong, *Anal. Chem.*, 2009, **81**, 1465; (d) L. Shang, L. Jin and S. Dong, *Chem. Commun.*, 2009, **45**, 3077; (e) L. Shang, C. Qin, L. Jin, L. Wang and S. Dong,

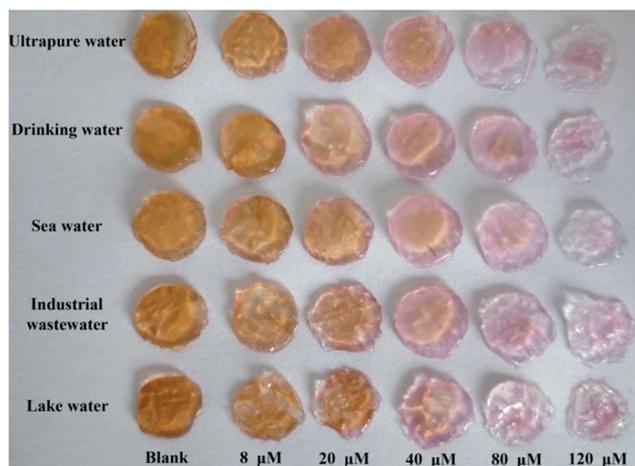


Fig. 5 Agarose gel "test strips" for the colorimetric detection of ultrapure, tap, sea, industrial, and lake water samples spiked with different concentrations of cyanide.

- Analyst*, 2009, **134**, 1477; (f) S. C. Wei, P. H. Hsu, Y. F. Lee, Y. W. Lin and C. C. Huang, *ACS Appl. Mater. Interfaces*, 2012, **4**, 2652; (g) Y. Zhai, L. Jin, P. Wang and S. Dong, *Chem. Commun.*, 2011, **47**, 8268; (h) X. Lou, Y. Zhang, J. Qin and Z. Li, *Chem.-Eur. J.*, 2011, **17**, 9691.
- 10 (a) X. Zhang, H. Wang and Z. Su, *Langmuir*, 2012, **28**, 15705; (b) L. Chuntonov, M. Bar-Sadan, L. Houben and G. Haran, *Nano Lett.*, 2012, **12**, 145; (c) Y. Ma, W. Li, E. C. Cho, Z. Li, T. Yu, J. Zeng, Z. Xie and Y. Xia, *ACS Nano*, 2010, **4**, 6725; (d) C. M. Gonzalez, Y. Liu and J. C. Scaiano, *J. Phys. Chem. C*, 2009, **113**, 11861.
- 11 (a) C. B. Norris, P. R. Joseph, M. R. Mackiewicz and S. M. Reed, *Chem. Mater.*, 2010, **22**, 3637; (b) J. B. Zeng, S. G. Fan, C. Y. Zhao, Q. R. Wang, T. Y. Zhou, X. Chen, Z. F. Yan, Y. P. Li, W. Xing and X. D. Wang, *Chem. Commun.*, 2014, **50**, 8121.
- 12 J. J. Du, B. W. Zhu and X. D. Chen, *Small*, 2013, **9**, 4104.
- 13 The average thickness of the silver shell was calculated using the following equation:  $t = (d_1 - d_2)/2$ ; where  $t$ ,  $d_1$  and  $d_2$  represent the thickness of the silver shell and the average diameter of Au@Ag core/shell NPs and Au NPs.
- 14 *Guidelines for Drinking-Water Quality*, World Health Organization, Geneva, 1996.
- 15 (a) S. Hajizadeh, K. Farhadi, M. Forough and R. E. Sabzi, *Anal. Methods*, 2011, **3**, 2599; (b) C. Radhakumary and K. Sreenivasan, *Analyst*, 2012, **137**, 5387.
- 16 C. Y. Liu and W. L. Tseng, *Chem. Commun.*, 2011, **47**, 2550.